

Porphyrin-Based Dye-Sensitized Solar Cells (DSSCs): a Review

Özgül Birel¹ · Said Nadeem^{1,2} · Hakan Duman³

Received: 12 December 2016 / Accepted: 3 February 2017 / Published online: 16 February 2017
© Springer Science+Business Media New York 2017

Abstract The current review aims to collect short information about photovoltaic performance and structure of porphyrin-based sensitizers used in dye-sensitized solar cells (DSSC). Sensitizer is the key component of the DSSC device. Structure of sensitizer is important to achieve high photovoltaic performance. Porphyrin derivatives are suitable for DSSC applications due to their thermal, electronic and photovoltaic properties. It describes some electrochemical and spectral properties as well as the structure of porphyrin dyes used in dye based-solar cells.

Keywords Porphyrin · DSSC · TiO₂ · Solar cells

Introduction

Nowadays, the world is facing major environmental problems such as pollution, global warming, overpopulation, natural resource depletion, waste disposal, climate changes, deforestation, ozone layer depletion, acid rain, public health

issues [1]. People are aware and cautious about the environmental issues. One of the main problems is the depletion of natural resource that force us to think and plan for various renewable energy sources [2] – energy that is based on solar, biomass, wind power, geothermal etc [1]. Although various fossil fuel resources such as oil, coal and natural gas are the largest energy sources for our living and production, these are not renewable. Sun is direct or indirect renewable energy source. Solar energy can be used directly to heat and light homes, generating electricity, and heatwater. Solar-to-electric energy conversion can play an important role to replace fossil fuels [2].

Sunlight is the most abundant, cleanest, cheap and safe energy source [3, 4]. Photovoltaic cells are used to convert sunlight into electric power. Commonly used photovoltaic cells are made of silicon (Si), cadmium telluride (CdTe), copper indium selenide/sulfide (CIS), perovskite solar cell and dye sensitized solar cells (DSSC) [1]. In 1991, Gratzel and his team developed DSSC known as Gratzel cell. In his cells, dye molecules were used as light absorber on the nanocrystalline film of titanium dioxide (TiO₂) [5]. DSSCs have attracted the attention of scientists as an alternative to the conventional photovoltaic cell due to their low production costs from sun light [6, 7], high power conversion efficiency [6], simplicity of fabrication [8] and tunable optical properties [9].

In the present review, we summarized the results from literature on the use of DSSC material of porphyrin derivatives as light absorber and DSSC in four contexts:

1. Structure of DSSC
2. Working Principle of DSSC
3. Some Porphyrin Derivative Dyes used in DSSC
4. Literature information of porphyrin derivatives for DSSC applications

✉ Said Nadeem
said81nadeem@yahoo.com

¹ Faculty of Sciences, Department of Chemistry, Muğla Sıtkı Koçman University, Kötekli, -48121 Muğla, Turkey

² Department of Medicinal and Aromatic Plants, Köyceviz Vocational School, Muğla Sıtkı Koçman University, Koyceğiz, 48000 Muğla, Turkey

³ Luleburgaz Higher Vocational School, Kırklareli University, Luleburgaz-39750, Kırklareli, Turkey

Structure of DSSC

The typical DSSC is a sandwich structure device having four major parts:

- 1) a photoanode composed of a nanocrystalline semiconductor film such as TiO_2 on a conducting glass substrate
- 2) monolayer of a sensitizer, normally a dye, adsorbed on the TiO_2 surface
- 3) electrolyte containing a redox couple such as I^-/I_3^-
- 4) a cathode

TiO_2

A porous layer of titanium dioxide (TiO_2) nanoparticles having wide band gaps suitable to generate useful voltage. Titanium dioxide (TiO_2) exists in three forms i.e. rutile, anatase and brookite. Although rutile is more stable, crystalline anatase is favoured as it is chemically more active in DSSCs [10]. The TiO_2 is a semiconductor that has a wide band gap ($E_{\text{bg}} \sim 3.2 \text{ eV}$) [11]. It is low in cost, widely available, biocompatible, cheap, thermally stable, chemically inert and non-toxic. In a typical DSSC, the particle size of TiO_2 anatase ranges 10–25 nm with a film thickness of 5–15 μm . Figure 1 shows various semiconductor oxides have similar energy band structure as that of TiO_2 .

There are several alternatives to TiO_2 . Zinc oxide (ZnO) is a promising alternate to TiO_2 because of its similar band structure and relatively high electron mobility [10]. Shalini et al. prepared ZnO films on a conducting glass substrate showed an efficiency of 0.4%. Higher electronic mobility of ZnO makes it more suitable for use in DSSC, but they have lesser life time due to the degradation of organic dyes under sunlight, increasing temperature, oxygen absorption, chemical change of electrodes and interface instability [11].

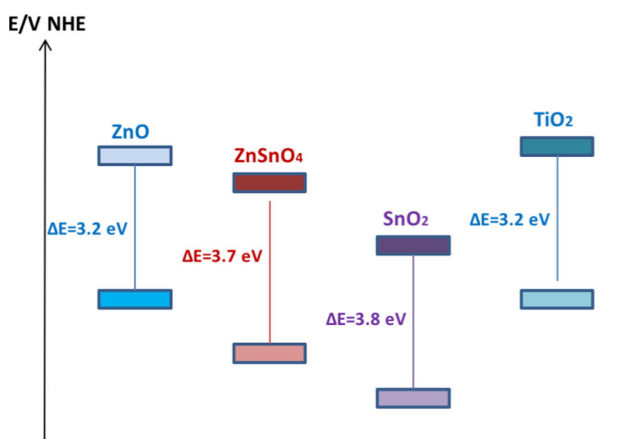


Fig. 1 Band gaps of various semiconductor oxides

Tin oxide (SnO_2) is another semiconductor oxide that has high mobility and large band gap i.e. 3.8 eV as compared to TiO_2 (3.2 eV). It creates fewer oxidative holes in the valence band under ultraviolet light thereby reduce the dye degradation rate and improve the stability of DSSCs. More positive band edge position facilitates electron injection from photoexcited dye molecules. The performance of SnO_2 -based DSSCs have been observed far much less than that of TiO_2 based ones. Particles of TiO_2 that are used as a photoanode to absorb sunlight are well-known n-type semiconductor that provides more surface to adsorb dye, accept electrons from the excited dye and conducts them towards the external circuit.

Dye

A dye, called as sensitizer is covalently bonded to the surface of the mesoporous oxide layer to enhance light absorption [10]. The dye acts as molecular electron pump in DSSC [11] by absorbing visible light, generating excited electrons and pumping them into the semiconductor [12].

The sensitizers used in the DSSC can be divided into organic and inorganic. Inorganic dyes contain a transition metal in the structure [6]. Polypyridyl ruthenium complexes had been regarded as the most efficient sensitizers and an overall light to electric power conversion efficiency (η) of up to 11% was achieved by using N719 (Di-tetrabutylammonium cis-bis(isothiocyanato)bis(2,2'-bipyridyl-4,4'-dicarboxylato) ruthenium(II)) -based DSSCs. However, since ruthenium is a rare metal, it is expensive and environmental issues caused by the production of ruthenium complexes limit its applications [13].

The dye must have certain properties to be suitable for application in DSSCs e.g. strong absorption in the visible range, high photo and thermal stability [11], good adsorption on the semiconductor's surface, that is, bonding strongly to the semiconductor surface with anchoring group, high solubility in the corresponding solvent, no toxicity, have a broad absorption spectrum in the visible range in order to capture solar radiation, a suitable high redox potential for regeneration followed by excitation [6, 14].

Many organic dyes such as porphyrine, coumarins, perylenes, phthalocyanines, triaryl amines and carbazole have been paid great attention because of their modest cost, large molar absorption coefficients and satisfactory stability [15]. Organic dyes can be classified into donor-acceptor (D-A), donor-bridge-acceptor (D-B-A) and acceptor-bridge-acceptor (A-B-A) systems that have applications as electroactive and photoactive materials in the field of molecular electronics; mainly photovoltaic technologies [16]. Bonding to TiO_2 surface has been achieved through functional groups such as salicylate, carboxylic acid, sulphonic acid, phosphonic acid and acylacetate derivatives [17]. So, the functional group of π -extended dye is vital to adsorb on the surface of TiO_2 . Carboxylic acids are the most extensively studied

anchoring groups in porphyrin-sensitized solar cells. They promote strong electronic coupling between the energy levels of the excited sensitizer and the metal oxide, that results in fast and efficient electron injection.

Electrolyte

An electrolyte, mostly iodide-tri-iodide, undergoes redox reaction. The efficiency of DSSCs depends on the sensitizers, photoanode and counter electrode [19]. Also electrolyte is very important to determine cell performance. So the electrolyte is one of the key components in DSSCs. Electron injection depends on the reducing ability of the electrolyte [11, 20]. It provides internal electric ion conductivity by diffusing within the mesoporous TiO₂ layer. Electrolyte contains a redox couple (such as I⁻/I₃⁻) that fills the space between the two electrodes [12]. Based on their physical state, the electrolyte used in DSSCs can be divided into three types: liquid, quasi and solid. Liquid electrolytes could be divided into organic solvent electrolyte and ionic liquid electrolytes according to the solvent used. Iodide/triiodide-based liquid electrolyte being redox electrolyte has been the most widely used and efficient electrolyte [21, 22].

Counter Electrode, Platinum (Pt)

Platinum (Pt) is typically used as a counter electrode to catalyze the triiodide ions that are formed in the electrolytes by the reduction of iodide ions. Although Pt has higher energy conversion efficiencies, it has few limitations such as higher cost, instability in redox electrolyte, high temperature sintering and resource scarcity. The open circuit voltage in DSSCs is determined by the energy difference between the fermi levels of the transparent conducting oxide (TCO) to the nanocrystalline TiO₂ film and the counter electrode. An ideal counter electrode (CE) should have low electrical resistance and high electro-catalytic activity towards the iodide/triiodide redox reaction, being stable and transparent [11].

Working Principle of Dye-Sensitized Solar Cells

Dye-derived nanocrystalline titania films are used as photoanode while platinized counter electrode, filled with electrolyte solution of I₃⁻/I⁻ in organic solvent. Cell is illuminated through the TiO₂ side [20].

Upon light illumination:

1. Light adsorbed by sensitizer that are adsorbed on the surface of mesoporous TiO₂ layer excites an electron. Electrons of the sensitizer are photo-excited.
2. An electron from the excited dye injects into the conduction band (CB) of TiO₂.
3. The dye molecules that loose an electron gets oxidized
4. The free electron travels through the layer of TiO₂ and flow through the external circuit to arrive at the counter electrode
5. The electron converts I₃⁻ to I⁻. Then, the oxidized dye is reduced back to its neutral state electron donation from electrolyte containing usually the solution of an organic solvent or ionic liquid solvent containing I₃⁻/I⁻ redox system.
6. The iodide is regenerated by reduction of triiodide at the counter electrode.

By this way, circuit is completed and the process can continue without permanent chemical change [6, 23]. These processes are competed by recombination of the injected electrons, either with the oxidized dye or the electron acceptor of the redox couple (I₃⁻), resulting in the dark current of the solar cell, and by relaxation of the excited dye to its ground state by a non-radiative decay process [12].

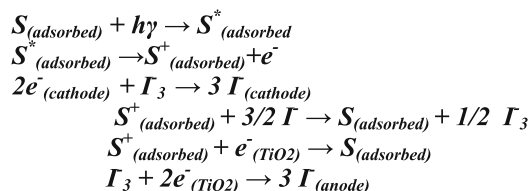


Fig. 2 Schematic diagram of a common DSSC [18]

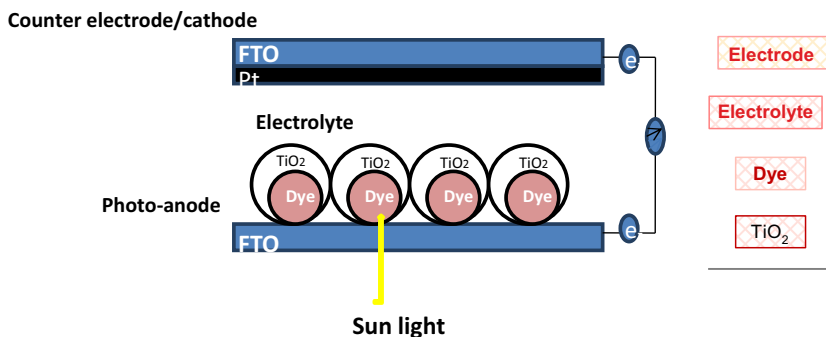


Table 1 Absorption and emissions of 4a, b and c porphyrin based dyes

Dye	Absorption	Emission
2	432, 569	620
3	424, 566	610
4	422, 557	600

Numbers in bold represents the molecules

Some Porphyrine Derivatives Used in Dye-Based Solar Cells

Porphyrin sensitizers have attracted a great deal of attention in solar cells as they are cheap, easy to synthesize and modify, stable [24], less toxic [25, 26], rigid geometry, the ability to coordinate metals, efficient electron transfer [27] etc. They also possess high molar absorption coefficients [28] and excellent light harvesting potential. Porphyrins absorb in visible and near infrared (NIR) region of solar spectrum i.e. intense Soret absorption band (400–450 nm) in the blue region and moderate Q absorption bands (500–650 nm) in the red region [26, 29–33]. The energy of LUMO orbitals of porphyrin is above the conduction band of TiO₂ while its HOMO level is below the redox couple of the electrolyte solution [34].

Porphyrins (Pors) are macrocycles consists of four pyrrole rings fused together. They are highly conjugated systems of 20 carbons and 4 nitrogens. It has 18- π electrons that makes them aromatic. The acidic NH protons located inside porphyrin ring can be deprotonated to yield porphyrinato anions. These rigid


and planar dianion species with a central cavity exhibits remarkable ligation characteristic towards metal cations [35]. Porphyrin can be derivatized at beta and meso positions as shown in Fig. 3.

Porphyrin molecules are used in various applications such as chemical and biological sensors in addition to DSSC, transistor and organic light emitting diodes [27]. The properties of porphyrin sensitizers can be tuned by modifying their donor, π -conjugate-bridge and acceptor [36]. Charge separation is an important factor that affects solar cell efficiency. It is formed in photoinduced charge transfer between the donor and acceptor. When the donor absorbs light energy, it injects an electron into the LUMO of the acceptor [37].

Mikroyannidis et al. have synthesized meso-substituted carboxylic acid Zn-porphyrin molecule (P) as shown in Fig. 1. Molecule (1) has a Soret band at 427 nm and Q bands at 559 nm and 606 nm. Its absorption peak is broad and strong in the range of 300–750 nm. It is attributed to the extended conjugation of π -systems in the meso-positions of porphyrin. An intramolecular charge transfer (ICT) takes place between the electron donating central porphyrin core and the electron withdrawing terminal cyanovinylene 4-nitrophenyls. This group enhanced the solubility.

The LUMO and HOMO energy levels for P are -3.55 eV and -5.50 eV, respectively. The band gap value of 1 is 1.95 eV. The LUMO level of dye should be higher than the conduction band of TiO₂. The difference between that values must be higher than 0.2 eV for efficient electron injection.

Fig. 3 Working principle of DSSC

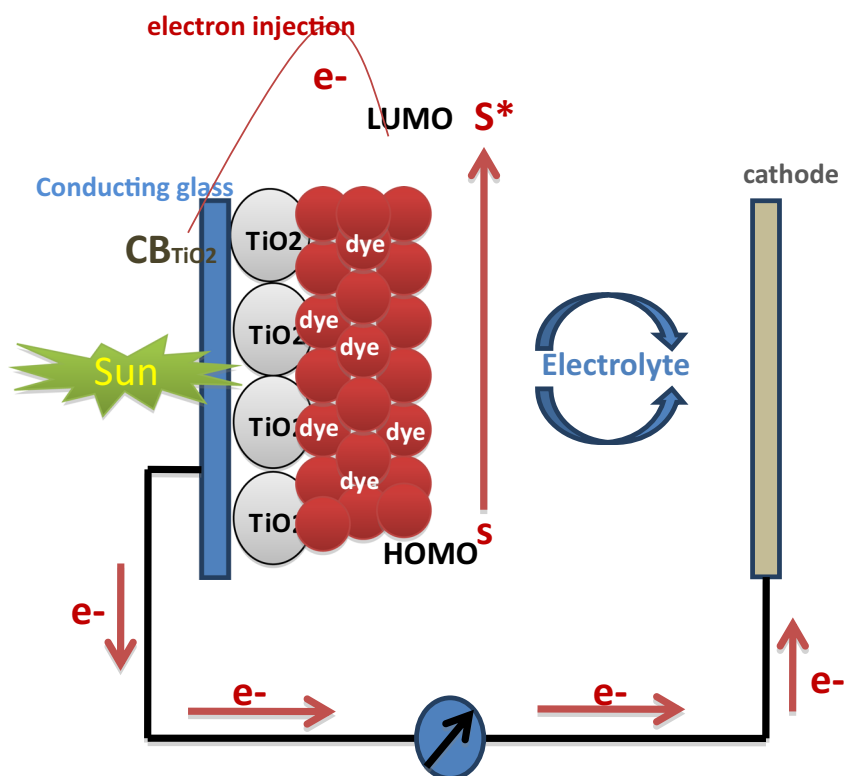

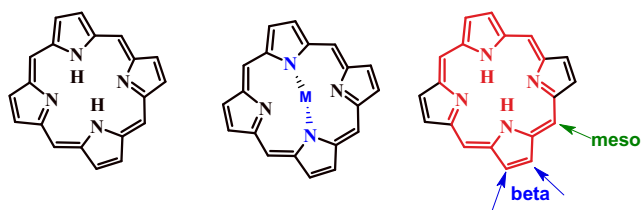


Fig. 4 Molecular structure of porphyrin (M: Zn²⁺, Cu²⁺, etc) [27]

The power conversion efficiency (PCE) of **1** is 2.90%. PCE has been improved up to 4.22% with addition of deoxycholic acid (DCA) to the solution of **1** for TiO₂ sensitization. Dye aggregation or close Π - Π^* stacking causes the charge recombination. Also, the lower charge collection efficiency or lower incident photons to current efficiency (ICPE) is attributed to the charge recombination. IPCE is improved with coadsorption by using deoxycholic acid (DCA). Mikroyannidis et al. [26] reported that co-adsorption is necessary to break up the dye aggregates.

The structure of **1** molecule is highly conjugated that is important for red shift. Also, **1** molecule has two carboxylic acid groups at meso positions. But at the end of conjugate system, **1** molecule has nitro groups [26].

Y. Liangs et al. [38] have synthesized three types Zn-porphyrine molecule as shown in Fig. 2. The absorption of porphyrin molecules (**2**, **3**, **4**) has measured in dichloromethane. Molecules have typical Soret and Q bands. It is observed that the absorption spectrum of **3** and **4** is slightly blue shift compared to **4a** (Table 1).

The HOMO energy levels are -5.101 eV for **2**, -5.135 eV for **3**, -5.124 eV for **4** while LUMO energy levels are -3.117 eV for **2**, -3.079 eV for **3**, -3.144 eV for **4**. The HOMO energy levels of all molecules are lower than that of Γ/Γ^{3-} (-4.8 eV). Y. Liangs has reported that all sensitizers can be efficiently regenerated by taking electrons from the electrolyte after photooxidation. The power conversion efficiency of the stated molecules is 4.05% for **2**, 5.26% for **3** and 2.62% for **4**. The PCE of **3** is greater than that of **2** and **4**.

Molecules shown in Fig. 3 are highly conjugated and containing cyanoacetic acids. The carboxylate groups are strongly bonded to the TiO₂ surface. Synthesized porphyrin molecules have a donor- Π -acceptor (D- Π -A) system. Diphenylamine, iminodibenzyl or iminostilbene groups are introduced at porphyrin meso position as an electron donating group. The power conversion efficiency of **4b** molecule is greater than that diphenylamine and iminostilbene-substituted porphyrin sensitized

solar cells [39]. Dye should be strongly anchored on the surface of TiO₂ to decrease the interface resistance. Electrons in the dye molecule need be quickly separated from holes and injected to the photoanodes before recombining [39].

Sharma et al. [33] have synthesized Zn-porphyrine molecules as shown in Fig. 3. Porphyrin derivative molecule has in Soret band in the 400–450 nm and two weaker Q bands in the 520–650 nm region. These bands arise from the configurational interaction of two porphyrin Π - Π^* electronic transitions. The UV-vis absorption spectrum of molecule onto TiO₂ show similar absorption but broader. This is because of anchoring of the sensitizer through its carboxylic acid groups to TiO₂.

The LUMO energy levels are -3.07 eV. It is higher than the TiO₂ conduction band edge (-4.2 eV in vacuum). The efficiently electron injection from LUMO of excited dye molecule to conductive band of TiO₂ is possible. The HOMO energy level of **5** is -5.23 eV. This value is lower than the potential of the electrolyte redox couple Γ/Γ^{3-} (-4.8 eV). Therefore, dye regeneration is thermodynamically feasible and could compete efficiently with recapture of injected electrons by the dye radical cations.

The power conversion efficiency of molecule **5** is 4.72%. It is used in co-sensitization to improve the photovoltaic performance of DSSCs. Sharma used a tertiary aryl amine compound **6** with two ethynyl-pyridine substituents and a terminal cyano-acetic acid group as a co-sensitizer that improved the photovoltaic performance by 7.34% [33].

Lu et al. [19] have synthesized three types of Zn-porphyrine molecule based on alkynes (**7**, **8**, **9**) as shown in Fig. 4. The absorption spectra of all molecules are similar. While the B bands involving the transition from the ground state to the second excited state are at 454, 459 and 461 nm, Q bands involving from weak transition to the first excited state are at 670, 667 and 668 nm (Table 2).

The power conversion efficiency of **9** is 8.53%, **8** is 8.20%, and **7** is 6.87%. The results of the power conversion efficiency show that long chain groups on the meso position affect the cell performance [19].

The carboxylic acid groups provide efficient adsorption of the dye on the semiconductor surface. Also, it promotes electronic coupling between the donor levels of the excited chromophore and the acceptor levels of the TiO₂ [17].


Zhang et al. [13] have synthesized three types of Zn-porphyrine molecule containing bis(phenyl hexyl) ethers (**10**, **11**, **12**) as shown in Fig. 5. The oxidation potential of **10** is 0.29 eV, **11** is 0.32 eV while **12** is 0.34 eV (Table 3). The very slightly shift of the oxidation potentials suggest minimal influence of the number of meso-substituted anchor group and the type of anchor group on the porphyrins HOMO energy levels. The UV-Vis spectra of the porphyrin sensitizers show absorption between 400 and 650 nm due to Π - Π^* transitions on the conjugated macrocycle.

Table 2 Absorption and emission of dyes synthesized by Lu et al.

Dye	Absorption	Emission
7	454, 670	688
8	459, 667	682
9	461, 468	678

Numbers in bold represents the molecules

Fig. 5 Molecule P

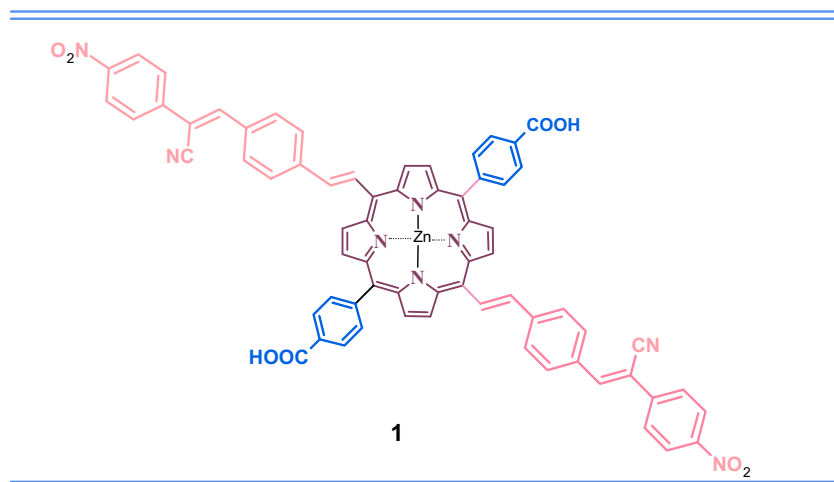

While the power conversion efficiency of 12 and 10 are 4.16% and 3.94%, respectively, the power conversion efficiency of 10 is 2.93%. It is probably due to the more effective conjugation of double bond in 12 with the porphyrin core than that of benzo group in 10 [13].

Three porphyrin derivatives include long alkoxy chains attached to the ortho positions of phenyl ring and a phenyl carboxylate acid or acrylic acid at the meso position. All porphyrin molecules were based on II-A-porphyrin system.

The phenyl group at meso position is conjugative linkage between the porphyrin and the binding group carboxylic acid. It is responsible to improve light harvesting performance. The double bonds at phenyl moiety are chosen as the conjugate linker.

Arrechea et al. [40] have synthesized two new porphyrin molecules that incorporate thiophene substituents (Fig. 6 13 and 14). Molecule 13 showed an intense Soret band (B band) at 471 nm and an intense intermolecular charge transfer (ICT) band at 662 nm. Also, one of the Q bands was observed at 583 nm between these bands. In 14, a new absorption band appeared at 523 nm with extension of the conjugation on the bridge by the introduction of a new thienylene-nevinylene unit. The ICT band was observed at 668 nm.

The potential energy of HOMO are -5.39 eV and -5.36 eV for 13 and 14, respectively. These values are lower than the potential of the electrolyte redox couple Γ/Γ^{3-} ($E_{\text{redox}} = -4.75$ eV). The E_{LUMO} values are -3.56 for 13 and -3.54 for 14. These values

Table 3 HOMO, LUMO, absorption and emission of Bis(phenyl hexyl) ethers based porphyrin dyes synthesized by Zhang et al.

Dye	HOMO Level	LUMO Level	Absorption	Emission
10	-5.09	2.83	421, 552, 591	598, 648
11	-5.12	2.91	428, 558, 594	609, 656
12	-5.14	3.00	433, 563, 611	626

Numbers in bold represents the molecules

show that efficient electron injection into to TiO_2 conduction band is energetically possible because of higher than the TiO_2 conduction band edge (-4.2 eV in vacuum).

The cell efficiency of 13 was found as 6.0% and 4.1% while 14 showed 4.7% and 5.0%. For two porphyrin molecule synthesized by Arrechea et al. where cyanoacrylate are anchoring group, thiophene substituents are spacers between the conjugated porphyrin core and the anchoring cyanoacrylate group [40].

Arteaga et al. [16] have synthesized a series of new porphyrin molecules as well as their application in dye-sensitized nanocrystalline TiO_2 solar cells (Fig. 7). The dyes exhibit strong Soret bands at 439–454 nm and weak Q bands between 574 and 664. Intramolecular charge transfer bands (ICT) occurred between the porphyrin core donor unit and the electron acceptors. An additional band around 350 nm corresponds to the $\Pi-\Pi^*$ transition was also found. The thiophene containing dyes 15–17 exhibit red-shifted when compared to the corresponding fluorene derivatives 18–20. This is attributed to the enhanced electronic coupling between the donor and acceptor entities in 15–17 due to the thiophene unit, which provides better conjugation than the fluorene moiety and lowers the energy of the charge transfer for conjugated dipolar molecules.

The HOMO energy level of the dyes have potentials ranging from 0.73 to 0.76 V, which are higher than that of the redox couple (~ -0.40 V). The LUMO energy levels of the dyes range from -1.07 to -1.20 V, lower than the energy level of the CB (conductive band) of TiO_2 (~ -0.5 V), with the energy gap of 0.57–0.70 V. It is well known that an energy gap of 0.2 eV is necessary for efficient electron injection.

DSSCs based on the dyes bearing a cyanoacrylic acid acceptor group showed the best photovoltaic performance and corresponds to an overall conversion efficiency of 5.56 and 4.13%, respectively. DiphenylamineZn(II) porphyrin behaves as core electron donor unit while the cyanoacrylic acid, rhodanine acetic acid, and dicyanorhodanine are acceptors.

Fig. 6 Y. Liangs et al. have synthesized three types Zn-porphyrine molecule

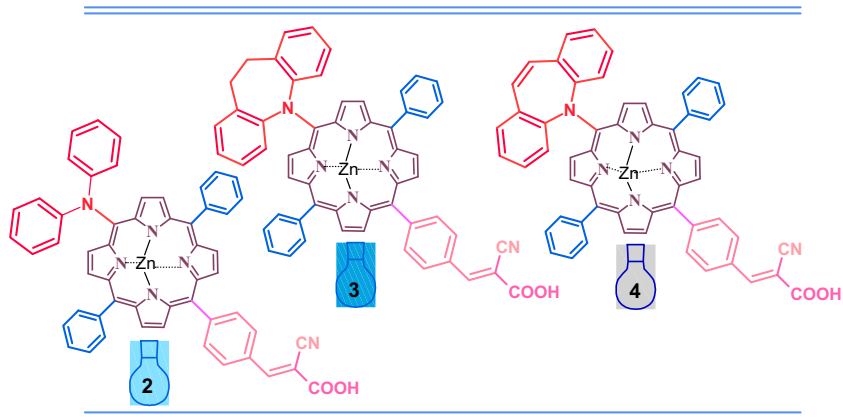


Fig. 7 Porphyrin derivative synthesized by Sharma et al. consists of a Zinc-metallated porphyrin unit covalently linked with a 1,3,5-triazine group and two terminal carboxylic acid groups of glycin

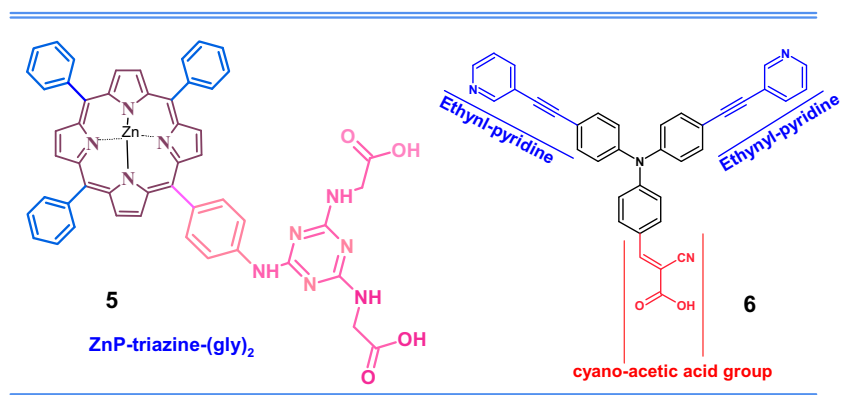
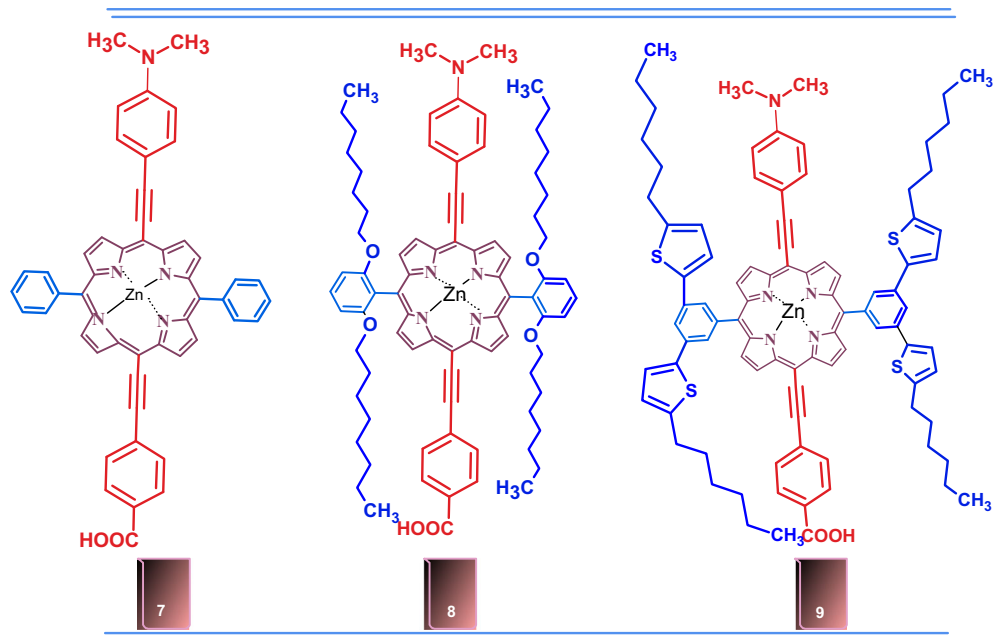


Fig. 8 Alkyne based dyes synthesized by Lu et al.



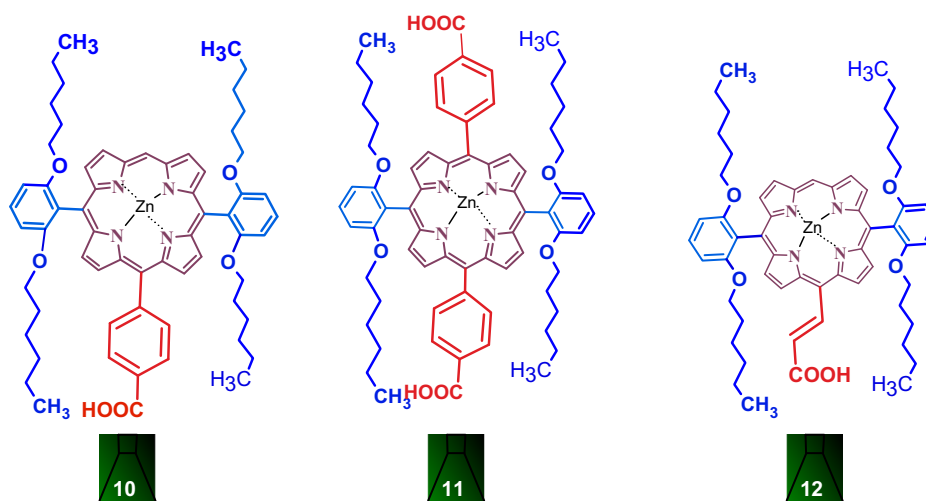


Fig. 9 Bis(phenyl hexyl) ethers based porphyrin dyes synthesized by Zhang et al.

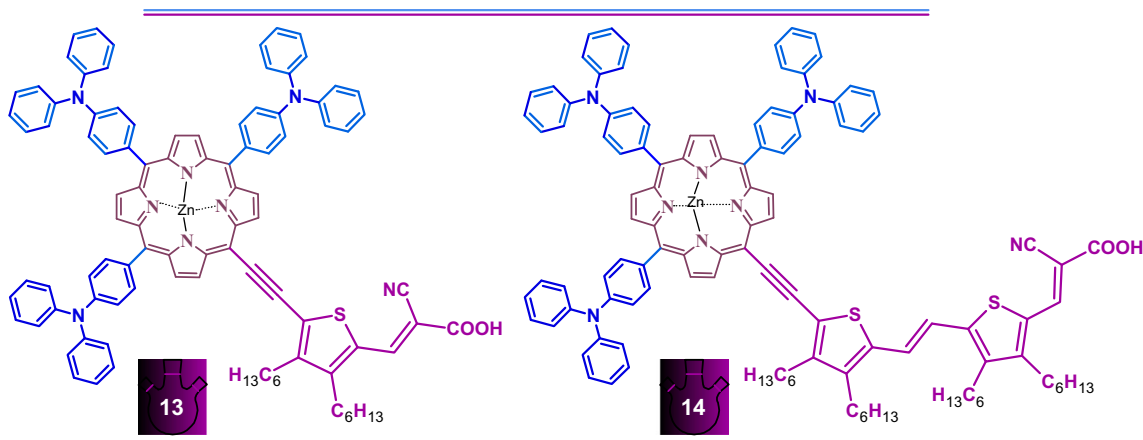


Fig. 10 Thiophene incorporated porphyrin based molecules synthesized by Arrechea et al.


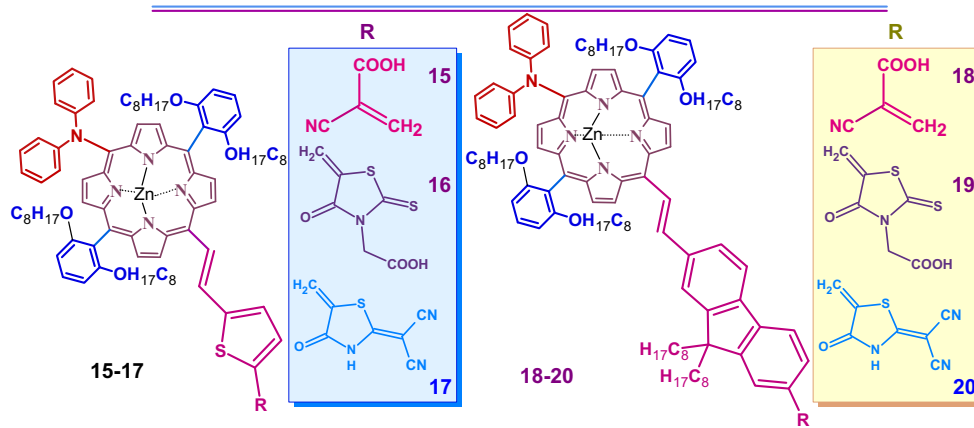


Fig. 11 Porphyrin derivatives synthesized by Arteaga et al.

Fig. 12 Molecular Structure and photovoltaic performance of some porphyrine derivatives

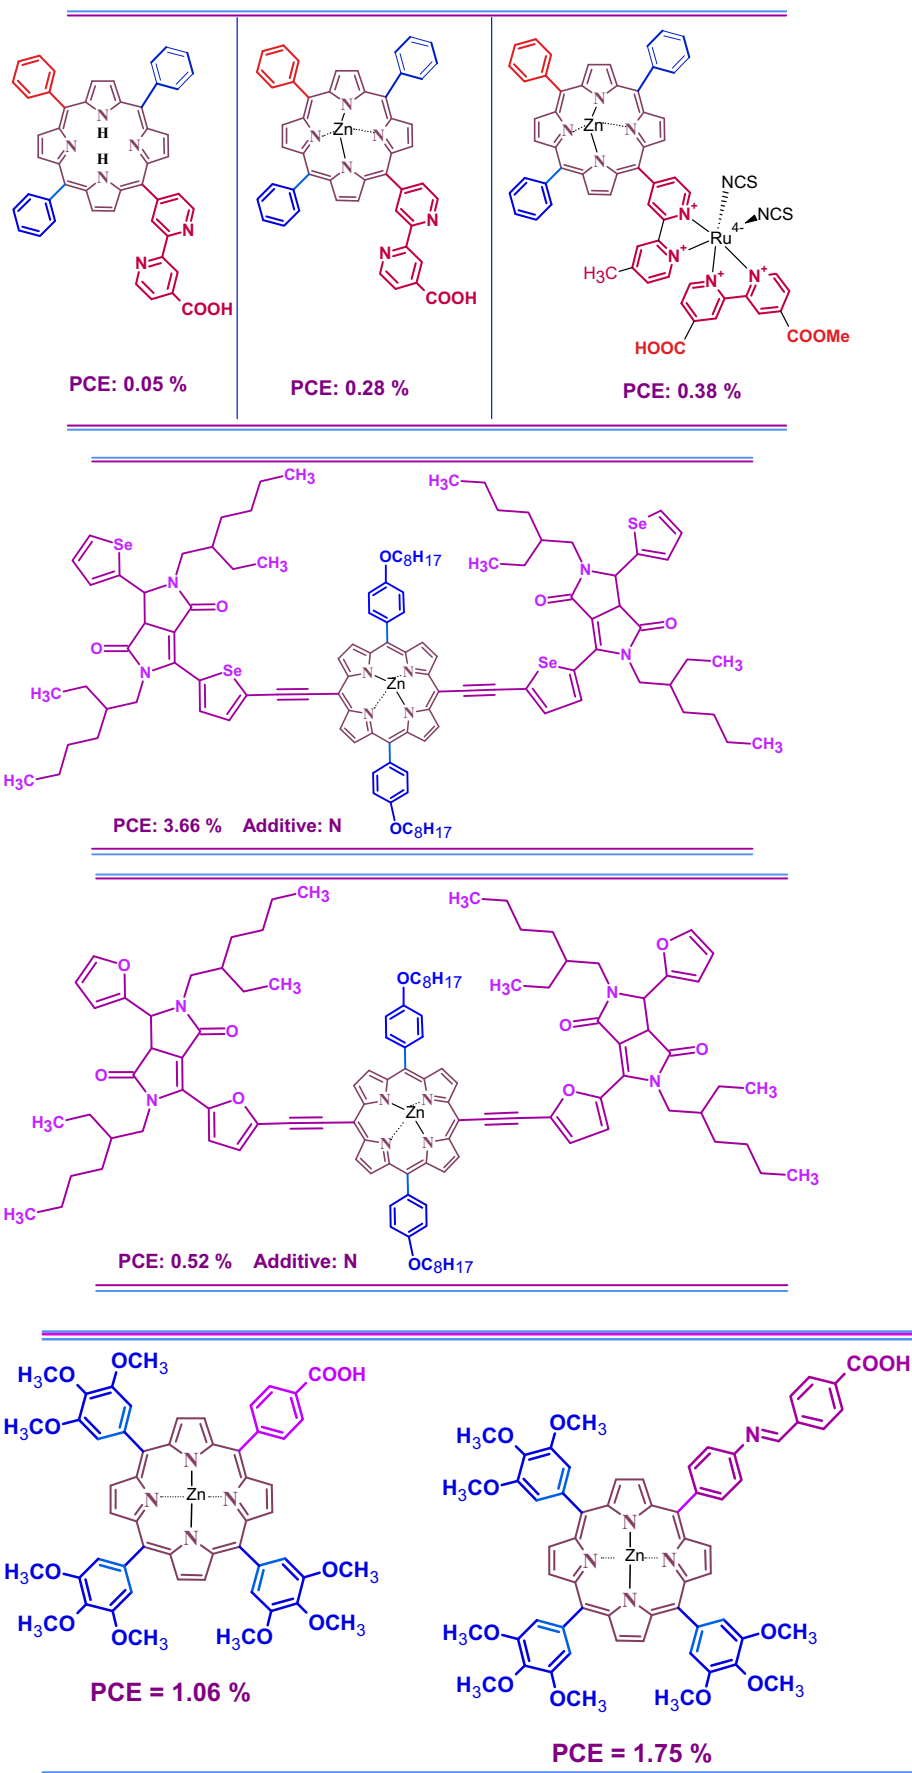

These electroactive units are linked by either vinyl-fluorene or vinyl-thiophene spacer units [16].

Few porphyrine-based porphyrins and their photovoltaic performance are shown in Fig. 8, 9, 10, 11 and 12 [41–43].

Conclusion

Various porphyrins, especially zinc complexes, have been used in DSSC preparation. Their LUMO energy levels are above the conduction band of the TiO₂ while HOMO energy levels are below the redox couple in the electrolyte solution. These require for charge separation at the TiO₂/dye/electrolyte surface. Metal free-porphyrin has low photovoltaic conversion efficiency than zinc-porphyrins. Porphyrins generally show lower performance due to the limited light absorption, poor matching to solar light distribution and consequently possess a low value of short circuit current. Generally, two methods are used to increase their performance i.e. elongating the Π system and lowering the symmetry of the macrocycle, which can lead to a significantly broadened Soret band and red shifted Q band absorptions. DSSC devices using porphyrin sensitizers with the linker and anchor units functionalized at the β -position is reported to show a value as high as 7.1%.

References

- Suait MS, Rahman MYA, Ahmad A (2015) Review on polymer electrolyte in dye-sensitized solar cells (DSSCs). *Sol Energy* 115:452–470
- Zhou W, Cao Z, Jiang S, Huang H, Deng L, Liu Y et al (2012) Porphyrins modified with a low-band-gap chromophore for dye-sensitized solar cells. *Organic Electronics: physics, materials, applications* 13:560–569
- Arrechea S, Molina-Ontoria A, Aljarilla A, De La Cruz P, Langa F, Echegoyen L (2015) New acceptor- π -porphyrin- π -acceptor systems for solution-processed small molecule organic solar cells. *Dyes Pigments* 121:109–117
- Panda MK, Ladomenou K, Coutsolelos AG (2012) Porphyrins in bio-inspired transformations: Light-harvesting to solar cell. *Coord Chem Rev*:2601–2627
- Zhang H, Zheng X, Li H, Jin B, Wang C, Shen Y et al (2013) Synthesis, photo-electrochemical properties and dye-sensitized solar cell performance of d- π -a structured porphyrins. *J Photochem Photobiol A Chem* 272:58–64
- Birel Ö (2015) An overview on the some phenothiazine derivative molecules used in organic dye-sensitized solar cells. *Electronic Journal of Vocational Colleges*
- Sharma GD, Daphnomili D, Angaridis PA, Biswas S, Coutsolelos AG (2013) Effect of thiourea incorporation in the electrolyte on the photovoltaic performance of the {DSSC} sensitized with pyridyl functionalized porphyrin. *Electrochim Acta* 102:459–465
- Apostolopoulou A, Karageorgopoulos D, Rapsomanikis A, Stathatos E (2016) Dye-sensitized solar cells with zinc oxide nano-structured films made with amine oligomers as organic templates and gel electrolytes. *Journal of Clean Energy Technologies* 4(5):311–315
- Mathew S, Yella A, Gao P, Humphry-Baker R, Curchod Basile FE, Ashari-Astani N et al (2014) Dye-sensitized solar cells with 13% efficiency achieved through the molecular engineering of porphyrin sensitizers. *Nat Chem* 6(3):242–247
- Gong J, Liang J, Sumathy K (2012) Review on dye-sensitized solar cells (DSSCs): fundamental concepts and novel materials. *Renew Sust Energ Rev* 16:5848–5860
- Shalini S, Prabhu RB, Prasanna S, Mallick TK, Senthilarasu S (2015) Review on natural dye sensitized solar cells: operation, materials and methods. *Renew Sust Energ Rev* 51:1306–1325
- Angaridis PA, Lazarides T, Coutsolelos AC (2014) Functionalized porphyrin derivatives for solar energy conversion. *Polyhedron* 82:19–32
- Zhang N, Zhang B, Yan J, Xue X, Peng X, Li Y et al (2015) Synthesis of π -A-porphyrins and their photoelectric performance for dye-sensitized solar cells. *Renew Energy* 77:579–585
- Grätzel C, Zakeeruddin SM (2013) Recent trends in mesoscopic solar cells based on molecular and nanopigment light harvesters. *Materials Today* 16:11–18
- Zeng Z, Zhang B, Li C, Peng X, Liu X, Meng S et al (2014) A key point of porphyrin structure affect {DSSCs} performance based on porphyrin sensitizers. *Dyes Pigments* 100:278–285
- Arteaga D, Cotta R, Ortiz A, Insuasty B, Martin N, Echegoyen L (2015) Zn (II)-porphyrin dyes with several electron acceptor groups linked by vinyl-fluorene or vinyl-thiophene spacers for dye-sensitized solar cells. *Dyes Pigments* 112:127–137
- Campbell WM, Burrell AK, Officer DL, Jolley KW (2004) Porphyrins as light harvesters in the dye-sensitized TiO₂ solar cell. *Coord Chem Rev* 248(13):1363–1379
- Hug H, Bader M, Mair P, Glatzel T (2014) Biophotovoltaics: natural pigments in dye-sensitized solar cells. *Appl Energy* 115:216–225
- Lu J, Liu S, Shen Y, Xu J, Cheng Y, Wang M (2015) Alkyl-thiophene functionalized D- π -a porphyrins for mesoscopic solar cells. *Electrochim Acta* 179:187–196
- Nwanya A, Ezema F, Ejikeme P (2011) Dyed sensitized solar cells: a technically and economically alternative concept to pn junction photovoltaic devices. *International Journal of the Physical Sciences* 6(22):5190–5201
- Sengupta D, Das P, Mondal B, Mukherjee K (2016) Effects of doping, morphology and film-thickness of photo-anode materials for dye sensitized solar cell application—a review. *Renew Sust Energ Rev* 60:356–376
- Kong F-T, Dai S-Y, Wang K-J (2007) Review of recent progress in dye-sensitized solar cells. *Advances in Opto Electronics* 2007
- Xie M, Wang J, Ren J, Hao L, Bai F-Q, Pan Q-J et al (2015) Theoretical study on a high-efficient porphyrin-sensitizer in a local electric field: how does the local electric field affects the performance of dye-sensitized solar cells? *Org Electron* 26:164–175
- Zhang X, Chen Q, Sun H, Pan T, Hu G, Ma R et al (2014) Theoretical design and screening of alkyne bridged triphenyl zinc porphyrins as sensitizer candidates for dye-sensitized solar cells. *Spectrochim Acta A Mol Biomol Spectrosc* 118:564–571
- Daphnomili D, Sharma G, Biswas S, Thomas KJ, Coutsolelos A (2013) A new porphyrin bearing a pyridinylethynyl group as sensitizer for dye sensitized solar cells. *J Photochem Photobiol A Chem* 253:88–96
- Mikroyannidis J, Charalambidis G, Coutsolelos A, Balraju P, Sharma G (2011) Novel zinc porphyrin with phenylenevinylene meso-substituents: synthesis and application in dye-sensitized solar cells. *J Power Sources* 196(15):6622–6628
- Narra VK, Ullah H, Singh VK, Giribabu L, Senthilarasu S, Karazhanov SZ et al (2015) D- π -a system based on zinc porphyrin

- dyes for dye-sensitized solar cells: combined experimental and DFT–TDDFT study. *Polyhedron* 100:313–320
28. Chen B, Sun L, Xie Y-S (2015) Modulation of photovoltaic behavior of dye-sensitized solar cells by electron donors of porphyrin dyes and cosensitization. *Chin Chem Lett* 26(7):899–904
 29. Chitpakdee C, Namuangruk S, Suttisintong K, Jungsuttiwong S, Keawin T, Sudyoadsuk T et al (2015) Effects of π -linker, anchoring group and capped carbazole at meso-substituted zinc-porphyrins on conversion efficiency of DSSCs. *Dyes Pigments* 118:64–75
 30. Zhou W, Zhao B, Shen P, Jiang S, Huang H, Deng L et al (2011) Multi-alkylthienyl appended porphyrins for efficient dye-sensitized solar cells. *Dyes Pigments* 91(3):404–412
 31. Sharma G, Zervaki G, Angaridis P, Vatikioti A, Gupta K, Gayathri T et al (2014) Stepwise co-sensitization as a useful tool for enhancement of power conversion efficiency of dye-sensitized solar cells: the case of an unsymmetrical porphyrin dyad and a metal-free organic dye. *Org Electron* 15(7):1324–1337
 32. Shalabi A, El Mahdy A, Taha H, Soliman K (2015) The effects of macrocycle and anchoring group replacements on the performance of porphyrin based sensitizer: DFT and TD-DFT study. *J Phys Chem Solids* 76:22–33
 33. Sharma GD, Angaridis PA, Pipou S, Zervaki GE, Nikolaou V, Misra R et al (2015) Efficient co-sensitization of dye-sensitized solar cells by novel porphyrin/triazine dye and tertiary aryl-amine organic dye. *Org Electron* 25:295–307
 34. Sirithip K, Morada S, Namuangruk S, Keawin T, Jungsuttiwong S, Sudyoadsuk T et al (2013) Synthesis and characterization of β -pyrrolic functionalized porphyrins as sensitizers for dye-sensitized solar cells. *Tetrahedron Lett* 54(19):2435–2439
 35. Alvarado MSA (2015) Novel porphyrin for DSSC and BHJ solar cells
 36. Zhang C-R, Han L-H, Zhe J-W, Jin N-Z, Shen Y-L, Gong J-J et al (2014) The role of terminal groups in electronic structures and related properties: the case of push–pull porphyrin dye sensitizers for solar cells. *Computational and Theoretical Chemistry* 1039:62–70
 37. Balanay MP, Dipaling CVP, Lee SH, Kim DH, Lee KH (2007) AM1 molecular screening of novel porphyrin analogues as dye-sensitized solar cells. *Sol Energy Mater Sol Cells* 91(19):1775–1781
 38. Liang Y, Xue X, Zhang W, Fan C, Li Y, Zhang B et al (2015) Novel D– π –a structured porphyrin dyes containing various diarylamino moieties for dye-sensitized solar cells. *Dyes Pigments* 115:7–16
 39. Basheer B, Mathew D, George BK, Nair CR (2014) An overview on the spectrum of sensitizers: the heart of dye sensitized solar cells. *Sol Energy* 108:479–507
 40. Arrechea S, Clifford JN, Pellejà L, Aljarilla A, de la Cruz P, Palomares E et al (2016) Charge recombination losses in thiophene-substituted porphyrin dye-sensitized solar cells. *Dyes Pigments* 126:147–153
 41. Tan Q, Zhang X, Mao L, Xin G, Zhang S (2013) Novel zinc porphyrin sensitizers for dye-sensitized solar cells: synthesis and spectral, electrochemical, and photovoltaic properties. *J Mol Struct* 1035:400–406
 42. Liang T, Xiao L, Liu C, Gao K, Qin H, Cao Y et al (2016) Porphyrin small molecules containing furan-and selenophene-substituted diketopyrrolopyrrole for bulk heterojunction organic solar cells. *Org Electron* 29:127–134
 43. Duanglaor P, Thiampanya P, Sudyoadsuk T, Promarak V, Pulpoka B (2015) Synthesis and photophysical properties of donor–acceptor system based bipyridylporphyrins for dye-sensitized solar cells. *Journal of Energy Chemistry* 24(6):779–785